



Kinetics of oxychlorination of chromite Part I. Effect of temperature

Ndue Kanari, I. Gaballah, Eric Allain

► To cite this version:

Ndue Kanari, I. Gaballah, Eric Allain. Kinetics of oxychlorination of chromite Part I. Effect of temperature. *Thermochimica Acta*, 2001, 371 (1-2), pp.143-154. 10.1016/S0040-6031(01)00414-2 . hal-01507428

HAL Id: hal-01507428

<https://hal.univ-lorraine.fr/hal-01507428>

Submitted on 10 May 2017

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Kinetics of Oxychlorination of Chromite : Part I. Effect of Temperature

N. KANARI, I. GABALLAH and E. ALLAIN*

Mineral Processing and Environmental Engineering team,
LEM^a, CNRS^b UMR 7569, ENSG^c, INPL^d, BP 40, 54501 Vandœuvre, France

* University of Missouri-Rolla, School of Mines and Metallurgy, Center for Pyrometallurgy
210 Fulton Hall, 65401 Rolla, MO, USA

Nonisothermal TG analysis was used to evaluate the reactivity of a chromite mineral $[(\text{Fe}^{2+}, \text{Mg})(\text{Cr}, \text{Al}, \text{Fe}^{3+})_2\text{O}_4]$ towards Cl_2+CO , Cl_2+N_2 and Cl_2+O_2 gaseous mixtures up to 1000 °C. Full chlorination and volatilization of reaction products were achieved at about 975 °C using Cl_2+CO , while only about 40 pct of the sample have reacted at 1000 °C using Cl_2+N_2 and Cl_2+O_2 .

The effect of the temperature on the oxychlorination with Cl_2+O_2 of the chromite mineral was studied between 600 °C and 1050 °C using isothermal TG measurements. The results show that the oxychlorination of chromite occurs in two stages. The initial stage of the oxychlorination was characterized by the average values of apparent activation energy of about 151 and 57 kJ/mol for the temperatures lower and higher than 825 °C, respectively. While a value of about 262 kJ/mol was found for the second stage of the oxychlorination process between 925 °C and 1050 °C. The effects of temperature on the oxychlorination of the simple chromite constituents (Cr_2O_3 , Fe_2O_3 and MgO) were also given.

a. Laboratoire Environnement et Minéralurgie, rue du Doyen M. Roubault, BP 40, 54501 Vandœuvre Cedex, France.

b. Centre National de la Recherche Scientifique, 3 rue Michel-Ange, 75794 Paris Cedex, France.

c. École Nationale Supérieure de Géologie, rue du Doyen M. Roubault, BP 40, 54501 Vandœuvre Cedex, France.

d. Institut National Polytechnique de Lorraine, 2 rue de la Forêt de Haye, 54501 Vandœuvre Cedex, France.

I. INTRODUCTION

Chlorination is an important step for the recovery of several metals such as Ti, Zr, Hf, Nb, Ta, rare-earth elements, etc. from their bearing materials. An overview concerning the applications and potential uses of chlorination methods in metallurgy of these metals was detailed by Korshunov^[1]. The author described the theoretical aspects of the chlorination, methods and apparatus used as well as the industrial application of the chlorine technology. As the majority of the above-mentioned elements occurred as oxides in earth crust, a reducing agent (C, CO) was added in the chlorination process to increase its efficiency.

However, the chlorination in the presence of oxygen (oxychlorination) was sometimes used to separate selectively a group of elements from the others. This is supported by the fact that the presence of the oxygen in the system could lead to different thermodynamic feasibility of the specific oxychlorination reactions. Recently, Gaballah and Djona^[2] proposed the chlorination with Cl₂+air of the spent hydrotreating catalysts in order to recover selectively Co, Ni, Mo, and V chlorinated compounds and to prevent the chlorination of the catalyst support (Al₂O₃). In previous investigations^[3-6], we used the oxychlorination for the upgrading of the chromite concentrates as well as for the partial recovery of chromium as chromium oxychloride (CrO₂Cl₂) almost pure.

This paper is devoted to the study of the effect of temperature on the oxychlorination of the chromite mineral in the absence of the mass transfer phenomenon. To our knowledge, no studies concerning the oxychlorination of chromite are reported in the literature.

II. MATERIALS AND EXPERIMENTAL PROCEDURE

The sample used in this study is a chromite mineral obtained from its concentrate described in details previously^[7]. Microprobe analyses revealed the following weight composition of this chromite mineral, considered as simple oxides : 59.4 pct Cr₂O₃, 13.9 pct FeO, 14.2 pct MgO, 9.5 pct Al₂O₃, and 0.1 pct SiO₂. The first four oxides are included in the chromite structure belonging to spinel one. Based on the microprobe data, the general formula of chromite sample could be given as : (Fe²⁺_{0.30}, Mg_{0.70})(Cr_{1.56}, Al_{0.37}, Fe³⁺_{0.07})O₄. On the other hand, this solid could be represented as the simple spinels of weight composition : 30.9 pct FeCr₂O₄, 51.0 pct MgCr₂O₄, 13.7 pct MgAl₂O₄ and 4.4 pct Fe₃O₄.

The thermogravimetric 'TG' chlorination tests were realized with 40 mg of the sample, using the experimental setup described earlier^[7]. Some oxychlorination tests, using several grams of sample, were carried out in a horizontal experimental setup described also in Reference [7].

III. RESULTS AND DISCUSSION

A. Nonisothermal TGA Treatment in Various Chlorinating Atmospheres

This study was started by nonisothermal TGA treatment of the chromite mineral in Cl_2+CO ($\text{Cl}_2/\text{CO} = 1$), Cl_2+N_2 ($\text{Cl}_2/\text{N}_2 = 1$), and Cl_2+O_2 ($\text{Cl}_2/\text{O}_2 = 4$) gaseous mixtures in order to evaluate its reactivity towards these chlorinating gaseous mixtures between 25 °C and 1000 °C. The heating rate of the sample was about 7 °C/min. Figure 1 (a) shows the evolution of the percent weight loss (PWL) of chromite sample as a function of temperature for the chosen gaseous mixtures and for the temperature higher than 400 °C. Almost sample was reacted with Cl_2+CO at temperatures approaching 975 °C while about 40 pct of the sample were chlorinated in Cl_2+N_2 and/or Cl_2+O_2 gas mixtures up to 1000 °C indicating a relatively low reactivity of chromite towards these chlorinating gaseous mixtures.

The derivative of weight loss versus temperature is reported in Figure 1 (b). Two maximums of reaction rate at about 655 °C and 890 °C are observed during the carbochlorination of the sample. The chlorination and the oxychlorination of chromite sample proceed with the maximal reaction rates at about 725 °C and 775 °C, respectively. Beyond these temperatures, the reaction rate decreases strongly with the increase of the temperature. The examination of Figures 1 (a) and (b) revealed that, at least, two different constituents of chromite possess different reactivities towards the three chlorinating gas mixtures. As the first approximation, it seems that Fe_3O_4 and FeCr_2O_4 (iron chromite) were the first to be reacted with reactive gases. The weight loss calculated for the chlorination of these compounds (refer to L_1^{Ch} in Figure 1 a) agrees with those obtained at about 900 °C during the chlorination using Cl_2+N_2 and Cl_2+O_2 gas mixture. MgCr_2O_4 (magnesium chromite) and MgAl_2O_4 appear to be more stable in chlorine in the absence of a reducing atmosphere. This is in good agreement with the thermodynamical predictions^[4]. In the case of the carbochlorination, CrCl_3 , $\text{FeCl}_{2/3}$, MgCl_2 , AlCl_3 are the most probable chlorides of the chromite reactions with Cl_2+CO . Details concerning the kinetics aspects of the chromite carbochlorination are given in a previous article^[7].

The main products of the chromite oxychlorination are expected to be CrO_2Cl_2 , FeCl_3 , and MgCl_2 . The evolution of the vapor pressure of chlorides as a function of the temperature is given in Figure 2^[8,9]. Concerning the oxychlorination, this figure suggests that the chromium oxychloride was volatile at low temperatures and ferric chloride possesses a vapor pressure of about one atmosphere at temperatures approaching 300 °C. On the other hand, using a Cl_2+O_2 with a Cl_2/O_2 molar ratio equal to 4 led to a volatilization rate of MgCl_2 higher than that magnesium chloride formation^[10]. Thus, the rate of the chlorides' volatilization will be higher than that of their formation during the oxychlorination of chromite and consequently the measured weight loss is directly related to the oxychlorination rate of the sample.

B. Isothermal TGA Treatment in Cl_2+O_2

1. Oxychlorination of chromite at 1050 °C

In attempt to obtain more information about the behavior of chromite oxychlorination, the isothermal treatment with Cl_2+O_2 gas mixture of a chromite ground sample and a sample of particle size of 125-180 μm was conducted at 1050 °C. The evolution of the sample PWL *versus* time is traced in Figure 3. The time scale is graduated in minutes up to 30 minutes and the rest of chlorination time is given in hours. About 35 pct of sample are chlorinated and volatilized for a reaction time less than 15 minutes. Then, the reaction rate falls sharply and about 12 hours are required to reach 88 PWL whereas the weight loss is stabilized. In both cases, the reaction rate is slightly affected by the particles' size.

The oxychlorination residues corresponding to the extent of reaction 'X' (ratio of weight of the reacted fraction to initial weight) equal to 0.40, 0.60, 0.80 and 0.88 (points a, b, c and d in Figure 3) were analyzed by scanning electron microscopy (SEM) and x-ray diffraction (XRD). The SEM spectrums of these residues, as well as that of the raw sample, are grouped in the Figure 4. The residue of point 'a' ($X = 0.40$) is free of iron but the full elimination of iron oxides can not justify a reaction extent of 0.40 as the iron oxides' content of the chromite is about 14 pct. Only the chlorination of both $FeCr_2O_4$ and Fe_3O_4 is in good agreement with an extent of reaction of 0.40 (refer to L_1^{Ch} in Figure 3). The SEM spectrums of points 'b' and 'c' show the decrease of Cr peak intensity and the increase of Mg and Al ones. Finally, the SEM spectrum of points 'd' is essentially composed of aluminum and magnesium without chromium. The evolution of elemental composition of residues from 'b' to 'd' indicates that $MgCr_2O_4$ could be chlorinated leaving the $MgAl_2O_4$ which is less reactive than others compounds of chromite towards Cl_2+O_2 gas mixture. The percent weight loss calculated (refer to L_2^{Ch} in Figure 3) for the chlorination of ($FeCr_2O_4+Fe_3O_4+MgCr_2O_4$) were in fair agreement with the observations of Figures 3 and 4. It is important to note that the chlorine is not detected in the chlorination residues. This confirmed the hypothesis that the reaction rate of chromite with Cl_2+O_2 was lower than that of the volatilization one of the generated products.

XRD diagrams of the residues corresponding to points 'a' to 'd' were almost similar. This is probably due to the fact that spinels ($FeCr_2O_4$, Fe_3O_4 , $MgCr_2O_4$, $MgAl_2O_4$) have the same crystalline structure and lattice parameters making difficult to distinguish them by XRD. Moreover, the removal simultaneous of the divalent (Fe^{2+} , Mg) and trivalent (Fe^{3+} , Cr) elements at same time from the chromite structure could compensate the ionic's radii effects on the lattice parameters.

2. Effect of gas flow rate

The effect of the gas flow rate on the reaction rate was assessed to determine the conditions under which the external mass phenomena could be minimized. A series of experiments was performed at 1000 °C using the Cl_2+O_2 gas mixtures with a Cl_2/O_2 molar ratio constant and equal to 4, while the total gas flow rate was varied from 15 to 75 L/h. Figure 5 (a) traces the evolution of the PWL as a function of the temperature. A dramatically decrease of the reactivity of sample after about 35 pct of weight loss was observed and it is almost not affected by the gas flow rate. Therefore, the evolution of reaction rate as a function of the gas flow rate was determined for the reaction extents $0.10 \leq X \leq 0.25$ and $0.40 \leq X \leq 0.50$ and it is shown in Figure 5 (b). It may be considered that the gas flow rate has almost not effect on the reaction rate for a gas velocity (V_g) higher than 40 cm/min. Therefore, a chlorinating gas mixture with a $V_g \approx 49.6$ cm/min was used for the determination of the temperature effect on the chromite oxychlorination.

3. Isothermal oxychlorination of chromite at different temperatures

A series of TGA experiments was carried out in the temperature range from 600 °C to 1050 °C. As the reaction rate was low for $X > 0.35$, the experiments carried out up to 900 °C are stooped when a reaction extent of 0.35 is approached. Figures 6 (a) and (b) trace the evolution of the PWL of the chromite sample *versus* time for several of isotherms performed for the reaction extents up to 0.30. It is clear from these figures that the time required to reach a given reaction extent decreases with the rise of the treatment temperature. The data of the isothermal oxychlorination of the chromite at temperatures higher than 900 °C and for reaction extents up to 0.80 are displayed in Figure 7 (d). As it shown, each curve undergoes a change in the slope at about $X = 0.35$ to indicate a sharp fall in the reaction rate. For instance, the reaction rate at 950 °C is drooped over 130 times.

The temperature dependency of the reaction rate was determined according to Arrhenius diagram. It was interesting to follow the evolution of apparent activation energy (E_a) as a function of reaction extent. The variation of E_a values with the reaction progress is shown in Figure 7 between 925 °C and 1050 °C. The value of E_a at the begging of the reaction is about 80 kJ/mol and decreases slightly with the progress of the reaction up to $X \leq 0.25$. An important increase of E_a is observed for $X > 0.35$ and the average value of activation energy is about 265 kJ/mol for $0.40 < X < 0.70$. It should be pointed out that the sudden change of activation energy coincides roughly with the chlorination of iron chromite : FeCr_2O_4 (refer to L_1^{Ch} in Figure 7). An example of Arrhenius diagram for the oxychlorination of chromite sample is shown in Figure 8. The apparent activation energy is calculated for $0.00 \leq X \leq 0.25$ between 600 °C and 1050 °C and for $0.40 \leq X \leq 0.50$ between 925 °C and 1050 °C. The oxychlorination of chromite for $X \leq 0.25$ is characterized by the average value of E_a of about 151 and 57 kJ/mol from 600 °C to 825 °C and from 825 °C to 1050

°C, respectively. As shown by Figure 8, the apparent activation energy for $0.40 \leq X \leq 0.50$ is about 262 kJ/mol. This high value of E_a indicates that the oxychlorination of magnesium chromite is strongly dependent on the temperature.

An attempt was made to fit mathematically the experimental data of the isothermal oxychlorination of the chromite. Different kinetics equations^[11] were used to describe mathematically the evolution of the reaction extent as function of time for the reaction extents lower and higher than 0.30. Eq. [1] seems to be the most appropriate to describe the evolution of the reaction extent ($X \leq 0.30$) as function of time for the oxychlorination of chromite between 600 °C and 800 °C. While, Eq. [2] matches well the oxychlorination data ($X \leq 0.30$) for the temperature ranges from 825 °C to 1050 °C (Figure 9 b). Similarly, Figure 9 (c) gives the data linearization by using Eq. [2] of the chromite oxychlorination isotherms for $X \geq 0.35$ between 925 °C and 1050 °C.

$$1-3(1-X)^{2/3}+2(1-X) = kt \quad [1]$$

$$X+(1-X)\ln(1-X) = kt \quad [2]$$

where k = constant and t = chlorination time.

Equations [1] and [2] are pertinent to represent pore diffusion control for the spherical and cylindrical pores' shape, respectively, if either the solid or the solid product are porous. Microscopic examination of the chromite samples at 1000 °C, for different reaction extents, showed that the particles become porous (cylindrical shape) with the progress of the reaction. On the other hand, the small dependency of the reaction rate on the particles' size of the sample (refer to Figure 3) is probably due to the porous formation inside the particles, thanks to gradual removing of iron and chromium from the chromite. This is also supported by the fact that the particle's size decreased little with the progress of the reaction for the reaction extent as higher as 0.80.

However, it is difficult to understand clearly the kinetics of the chromite oxychlorination due to complex composition and structure of the chromite. Thus, pore diffusion could occur simultaneously with chemical reaction inside the particles. To clarify some more the kinetics phenomena of the oxychlorination, another series of TGA tests of chromite oxychlorination was performed between 700 °C and 1040 °C using a Cl_2+O_2 gas mixture with a Cl_2/O_2 molar ratio equal to 0.5. In other words, the partial pressure of chlorine was decreased, leading probably to the decrease of the reactivity of the reactive gases and limiting the pore diffusion phenomena.

Figures 10 (a) and (b) assemble the experimental data obtained for the oxychlorination of chromite with Cl_2+O_2 ($\text{Cl}_2/\text{O}_2 = 0.5$) at $X \leq 0.30$. The effect of the temperature on the chromite oxychlorination, under the theses conditions, was determined by the Arrhenius diagram.

The Arrhenius diagrams of the oxychlorination of chromite ($X \leq 0.25$) for both oxychlorination gas mixtures are compared in Figure 11. Clearly, the reaction rate using Cl_2+O_2 with $\text{Cl}_2/\text{O}_2 = 4$ is higher than that obtained using Cl_2+O_2 with $\text{Cl}_2/\text{O}_2 = 0.5$ in whole temperature range explored. While, the values of the apparent activation energy at temperatures lower than 825 °C are similar in both cases. However, at temperatures higher than 825 °C, the value of the E_a in the case of using Cl_2+O_2 with $\text{Cl}_2/\text{O}_2 = 0.5$ is higher (85 kJ/mol) than that deduced when Cl_2/O_2 ratio in the gas mixture was 0.4. This increase in the value of the E_a could be probably due to the presence of a mixed regime, i.e., pore diffusion and chemical reaction inside the pores.

$$1-(1-X)^{1/2} = kt \quad [3]$$

where k = constant and t = chlorination time.

The mathematical fitting of the experimental data for the chromite oxychlorination with Cl_2+O_2 ($\text{Cl}_2/\text{O}_2 = 0.5$) is represented in Figure 12. As shown by Figure 12 (a), straight lines are obtained by fitting the experimental data using Eq. [1] at temperatures lower or equal to 800 °C. Figure 12 (b) gives the evolution of the reaction extent versus time related by Eq. [3] for the oxychlorination of chromite at temperatures equal or higher than 850 °C. This mathematical fit gathered with the value of E_a seem confirmed the mixed rate controlling step of the chromite oxychlorination with Cl_2+O_2 ($\text{Cl}_2/\text{O}_2 = 0.5$) at temperatures higher than 800 °C.

4. Effect of temperature on the oxychlorination of the simple chromite oxides

Although the simple oxides of chromite mineral are combined in the spinel structure (Fe^{2+} , $\text{Mg})(\text{Cr}, \text{Al}, \text{Fe}^{3+})_2\text{O}_4$, it was worthwhile to study the effect of temperature on the oxychlorination of simple oxides : Cr_2O_3 , $\text{Fe}_{(1-x)}\text{O}$, Fe_2O_3 , MgO and Al_2O_3 . Their composition and structures were determined by SEM and XRD analysis^[4]. The tests were carried out in boat experiments using the horizontal setup. Several grams were used for each test. An oxychlorinating gas mixture composed of Cl_2 +air with a Cl_2 /air molar ratio equal to 1 was used and the oxychlorination time was fixed at 2 hours. The results are given in Figure 13 as evolution of PWL versus time. This figure contains also the results of the oxychlorination of chromite in the same conditions used as for the simple oxides.

Details concerning the behavior of these oxides in the Cl_2+O_2 were given previously^[4]. Iron oxides are the most reactive towards the oxychlorinating gas mixture and almost full reaction was obtained at about 900 °C. The reaction product was identified as FeCl_3 . The reactivity of Cr_2O_3 seems to be lower than that of iron oxides especially at higher temperatures and the reaction product was chromium oxychloride (CrO_2Cl_2). Magnesium oxide seems to be inert up to about 850 °C and only 20 pct of sample had reacted at 1000 °C generating magnesium chloride. While, no reaction of aluminum oxide with the oxychlorinating gas mixture was observed even at 1000 °C. Chromite started to react with Cl_2 +air from about 600 °C and less than 30 pct of the sample had

reacted at 1000 °C during 2 hours. This series of experiments revealed roughly the reactivity of these oxides towards oxychlorinating gas mixtures as well as the main products of the reactions.

More consist information was obtained during the treatment of these oxides using TG measurements in the absence of the mass transfer phenomena. Wüstite ($\text{Fe}_{(1-x)}\text{O}$) was not tested because it transformed rapidly into hematite (Fe_2O_3) during the chlorination. Aluminum oxide was not taken into consideration due to its refractive nature towards chlorine in absence of a reducing atmosphere^[4].

The other oxides (Cr_2O_3 , Fe_2O_3 , and MgO) were oxychlorinated with Cl_2+O_2 gas mixture with Cl_2/O_2 molar ratio equal to 4. Kinetics aspects of the oxychlorination Cr_2O_3 and MgO were reported in Reference [12] and [10], respectively. Figure 14 compares the temperature effects on the oxychlorination of the chromite and its simple oxides. The following observations could be deduced from this figure :

1. Concerning the oxychlorination of chromite (first stage), Cr_2O_3 , and Fe_2O_3 :
 - a. chromite oxychlorination is characterized by a value of the apparent activation energy of about 151 kJ/mol between 600 °C and 825 °C. About the same value of the E_a (≈ 148 kJ/mol) was obtained for the hematite oxychlorination. Chromium (III) oxide oxychlorination proceeds with an E_a value of about 46 kJ/mol^[12] at temperatures higher than 700 °C. The reaction rate of chromite and that of hematite with Cl_2+O_2 at temperatures lower or equal to 800 °C are of the same order of magnitude. It may be speculated that for the first stage of the chromite (FeCr_2O_4) reaction with Cl_2+O_2 at temperatures ≤ 800 °C depended on the oxychlorination rate of iron oxides.
 - b. as at temperatures higher than 825 °C, the oxychlorination of chromite and that of Cr_2O_3 were characterized by the similar values of the E_a and reaction rates, it seems that the global reaction rate of chromite is affected by the oxychlorination rate of Cr_2O_3 .
2. Concerning the oxychlorination of chromite (second stage), Cr_2O_3 , and MgO :

the value of E_a deduced from the data of chromite ($X \geq 0.4$), Cr_2O_3 , and MgO oxychlorination are about 262, 46^[12] and 214 kJ/mol^[10], respectively. The reaction rate of Cr_2O_3 is much higher than that of chromite. Thus, it has be supposed that the oxychlorination of chromite for $X \geq 0.4$ (MgCr_2O_4) depended on the MgO reaction rate with Cl_2+O_2 as the reaction rates and the values of E_a are comparable.

Although these similarities of the chromite oxychlorination with the reactions of its simple oxides with Cl_2+O_2 , other phenomena such as : the chemical bonds between the simple oxides in the chromite spinel structure, the interaction between the reaction products and chromite, the formation of the lacunaire spinels, etc., are expected to affect the chromite oxychlorination.

IV. CONCLUSIONS

The presence of a reducing atmosphere was necessary to achieve a complete reaction of the chromite mineral with chlorine. Only iron chromite could be oxychlorinated at temperatures lower than 1000 °C using nonisothermal conditions.

The oxychlorination of the chromite occurred in two stages characterized by widely different reactivities of chromite towards Cl_2+O_2 gaseous mixture. Similarly, the effect of the temperature changed significantly with the progress of the reaction. Iron chromite seems to be more reactive than magnesium chromite in the oxychlorinating gases.

The oxychlorination of the chromite with Cl_2+O_2 ($\text{Cl}_2/\text{O}_2 = 4$) for the reaction extents up 0.30 proceeded with an apparent activation energy of about 151 and 57 kJ/mol for the temperatures ranges of 600 °C to 825 °C and 825 °C to 1050 °C. Oxychlorination with a Cl_2+O_2 mixture having a Cl_2/O_2 ratio of 0.5, at temperatures lower than 825 °C led to the similar temperature effect on the reaction rate. While a value of E_a of about 85 kJ/mol was obtained for the oxychlorination at temperatures higher than 825 °C. The oxychlorination rate using Cl_2+O_2 with $\text{Cl}_2/\text{O}_2 = 4$ is systematically higher than that obtained using a Cl_2+O_2 with $\text{Cl}_2/\text{O}_2 = 0.5$.

The second stage of the chromite oxychlorination ($X > 0.35$) is strongly dependent on the reaction temperature and it was characterized by a value E_a of about 262 kJ/mol between 925 °C and 1050 °C.

The effects of the temperature on the chromite oxychlorination may be roughly explained by the dependency of the temperature on the reaction of the simple chromite constituents.

ACKNOWLEDGMENTS

This work was performed in the frame of contract N° BRE2-CT92-0173 thanks to the financial support of the European Union (DG-XII). The authors thank Dr. H. L. Schmidt for discussion, suggestion and help.

They also would like to thank Dr. J. C. Mugica, Dr. R. Solozabal (INASMET, San Sebastian, Spain) and Dr. M. Coelho (INETI, Lisbon, Portugal) for technical discussions. Authors are indebted to Dr. A. Bonazébi, Dr. M. Djona, Dr. S. Ivanaj, Dr. N. Menad, Dr. N. Mirghaffari for discussions and help on different subjects and to Mrs. C. Richard for technical and administrative support.

REFERENCES

- 1 B.G. Korshunov: *Metallurgical Review of MMIJ*, 1992, Vol. 8, (2), pp. 1-33.
- 2 I. Gaballah and M. Djona: *Metall. Mater. Trans. B*, 1995, vol. 26B, pp. 41-50.
- 3 I. Gaballah: Fifth Report of European Union Contract No BRE2-CT92-0173, Institut National Polytechnique de Lorraine, Laboratoire Environnement et Mineralurgie, Nancy, France, October 1995.
- 4 N. Kanari: Ph.D. Thesis, Institut National Polytechnique de Lorraine, Laboratoire Environnement et Mineralurgie, Nancy, France, November 1995, 209 pages.
- 5 N. Kanari and I. Gaballah: Paper presented at Proc. of the TMS Annual Meeting, Orlando, Florida, February 9-13, 1997, EPD Congress 1997, Ed. by B. Mishra, Pub. by TMS, pp. 57-71.
- 6 N. Kanari and I. Gaballah: Paper presented at Proc. of the TMS Annual Meeting, San Antonio, Texas, February 15-19, 1998, Light Metals 1998, Ed. by Barry J. Welch, Published by TMS, pp. 1333 - 1341.
- 7 N. Kanari, E. Allain, and I. Gaballah: *Metall. Mater. Trans. B*, 1999, vol. 30B, pp. 577-587.
- 8 Anonymous : in Handbook of Chemistry and Physics, (66th edition, Eds. R.C. Weast, M.J. Astle, and W.H. Beyer, CRC Press, Boca Raton, Florida, USA, 1986), pp. D193 - D194.
- 9 P. Pascal : in Nouveau Traité de Chimie Minérale, Masson et C^{ie}, eds., 1959, tome XIV, p. 135.
- 10 N. Kanari, I. Gaballah, and E. Allain: *Metall. Mater. Trans. B*, 1999, *in press*.
- 11 J. Szekely, J.W. Evans and H.Y. Sohn, in Gas-Solid Reactions, Academic Press, New York, NY. 1976, pp. 68-70, 73-88, 109-131 and 232-240.
- 12 I. Gaballah, S. Ivanaj, and N. Kanari: *Metall. Mater. Trans. A*, 1998, vol. 29A, pp. 1299-1308.

Kinetics of Oxychlorination of Chromite : Part I. Effect of Temperature

N. KANARI, I. GABALLAH and E. ALLAIN*

Mineral Processing and Environmental Engineering Team,
LEM^a, CNRS^b UMR 7569, ENSG^c, INPL^d, BP 40, 54501 Vandœuvre, France

* University of Missouri-Rolla, School of Mines and Metallurgy, Center for Pyrometallurgy
210 Fulton Hall, 65401 Rolla, MO, USA

FIGURE CAPTIONS

- Figure 1 : Thermogravimetric analysis of chromite (*a*) in different chlorinating gas mixtures and (*b*) derivative of weight losses versus temperature.
- Figure 2 : Evolution of vapor pressure of several chlorides as a function of temperature^[8,9].
- Figure 3 : Isothermal oxychlorination with Cl_2+O_2 of two grain sizes of chromite at 1050 °C.
- Figure 4 : SEM results of oxychlorination residues of chromite at 1050 °C for different reaction extents.
- Figure 5 : Isotherms of the chromite oxychlorination using (*a*) different gas flow rate and (*b*) its effect on the reaction rate.
- Figure 6 : Isotherms of the chromite oxychlorination with Cl_2+O_2 between :
(*a*) : 600 °C and 800 °C ($X \leq 0.30$),
(*b*) : 850 °C and 1050 °C ($X \leq 0.30$),
(*c*) : 925 °C and 1050 °C ($X \leq 0.80$).
- Figure 7 : Evolution of the activation energy as a function of the reaction extent.
- Figure 8 : Example of Arrhenius plot of the chromite oxychlorination.
- Figure 9 : Mathematical fitting of the data of the chromite oxychlorination for :
(*a*) : $T \leq 800$ °C, $X \leq 0.30$ using Eq. [1],
(*b*) : $T \geq 825$ °C, $X \leq 0.30$ using Eq. [2],
(*c*) : $T \geq 925$ °C, $X \geq 0.35$ using Eq. [2].
- Figure 10 : Isotherms of the chromite oxychlorination with Cl_2+O_2 having a Cl_2/O_2 molar ratio equal to 0.5 for (*a*) $T \leq 800$ °C and (*b*) $T \geq 850$ °C.
- Figure 11 : Comparison of Arrhenius plots of the chromite oxychlorination with Cl_2+O_2 gaseous mixtures having different Cl_2/O_2 molar ratios.
- Figure 12 : Mathematical fitting of the oxychlorination data at (*a*) $T \leq 800$ °C and (*b*) $T \geq 850$ °C using Eqs. [1] and [3], respectively.
- Figure 13 : Oxychlorination of chromite and its simple oxides with Cl_2 +air between 600 °C and 1000 °C for 2 hours using boat experiments.
- Figure 14 : Comparison of Arrhenius plots of the oxychlorination of chromite, Fe_2O_3 , Cr_2O_3 , and MgO .

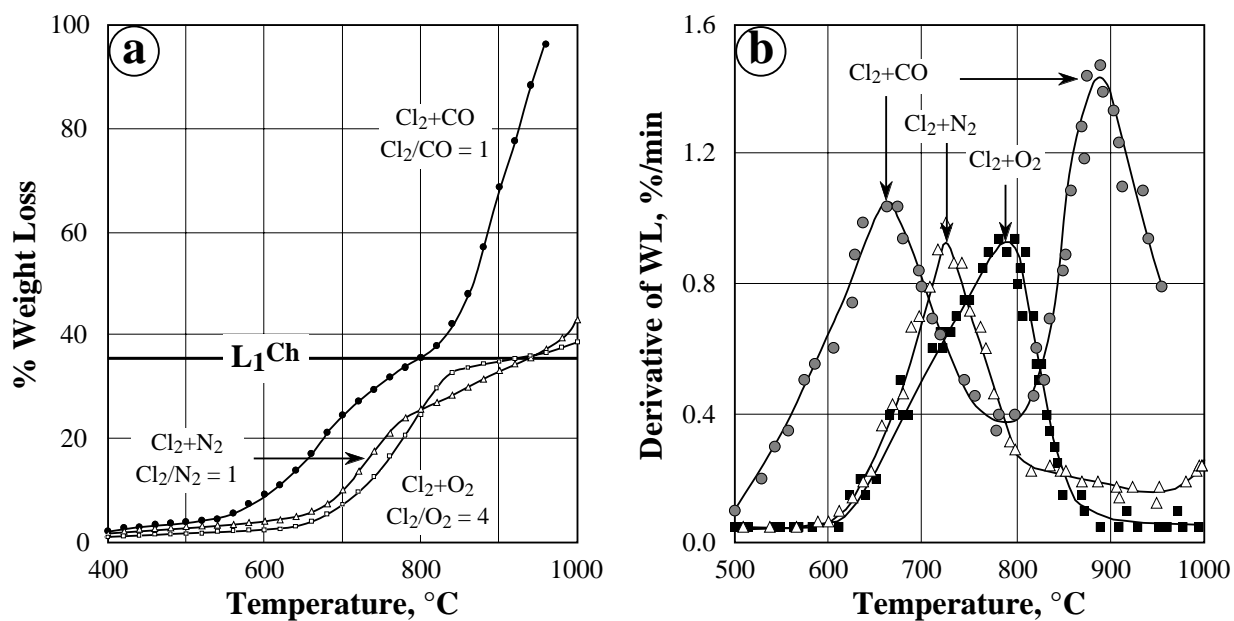


Figure 1 : Thermogravimetric analysis of chromite (*a*) in different chlorinating gas mixtures and (*b*) derivative of weight losses *versus* temperature.

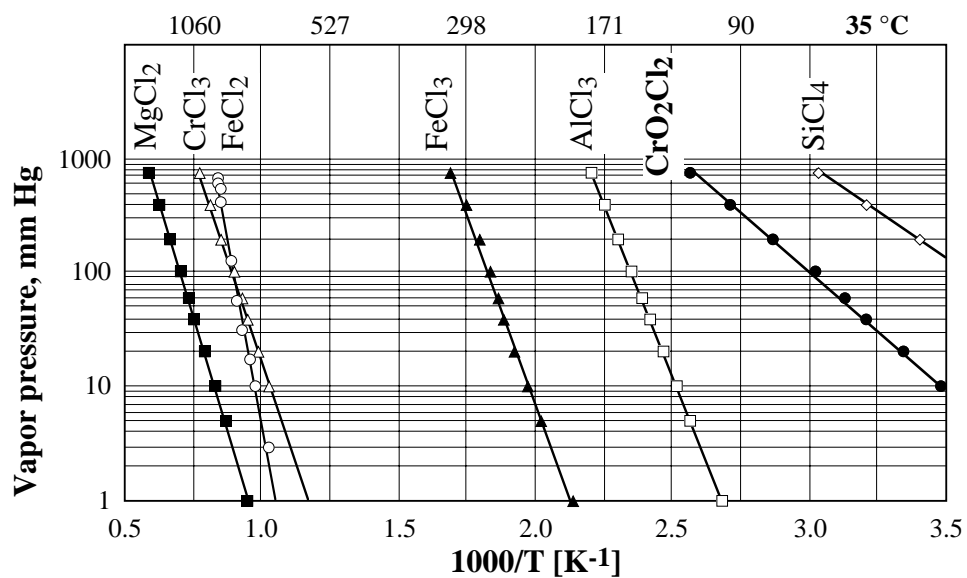


Figure 2 : Evolution of vapor pressure of several chlorides as a function of temperature^[8,9].


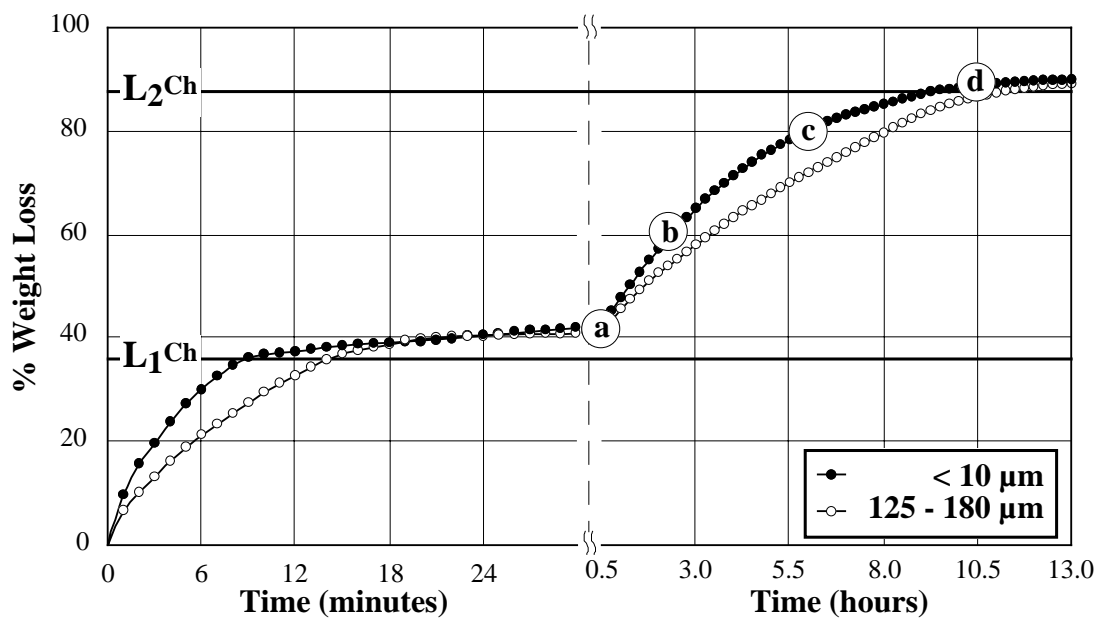


Figure 3 : Isothermal oxychlorination with $\text{Cl}_2 + \text{O}_2$ of two grain sizes of chromite at 1050 °C.

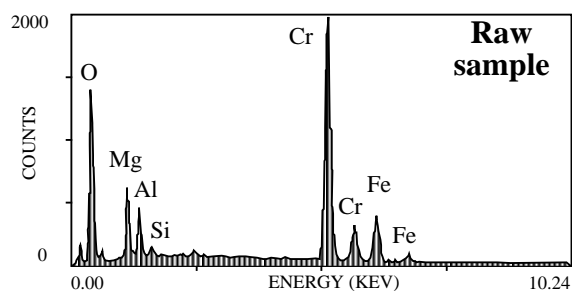

a : $X = 0.40$,

b : $X = 0.60$,

c : $X = 0.80$,

d : $X = 0.88$.

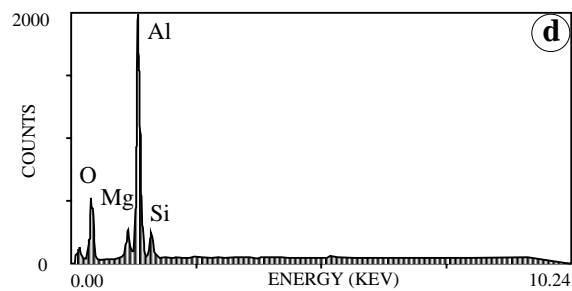
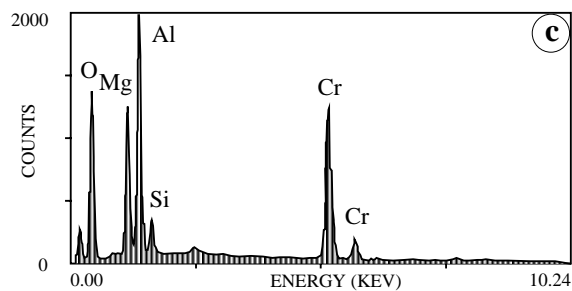
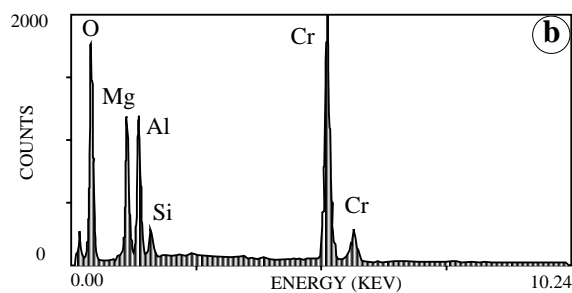
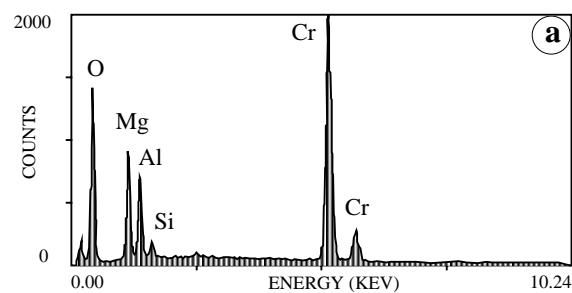


Figure 4 : SEM results of oxychlorination residues of chromite at 1050 °C for different reaction extents.

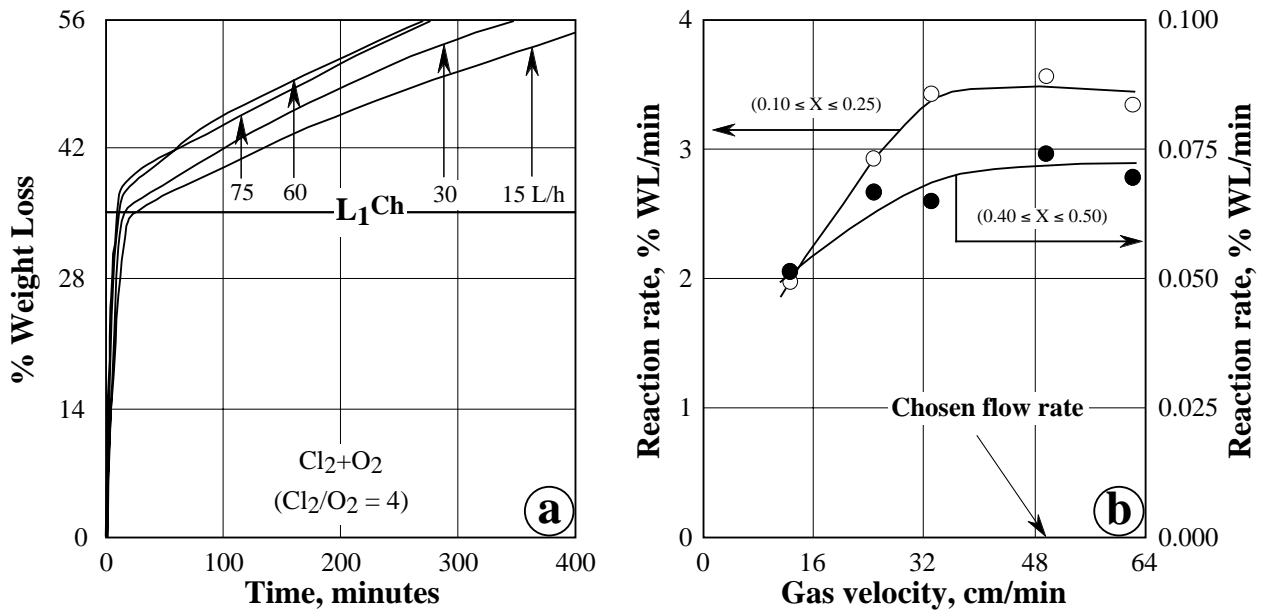


Figure 5 : Isotherms of the chromite oxychlorination using (a) different gas flow rate and (b) its effect on the reaction rate .

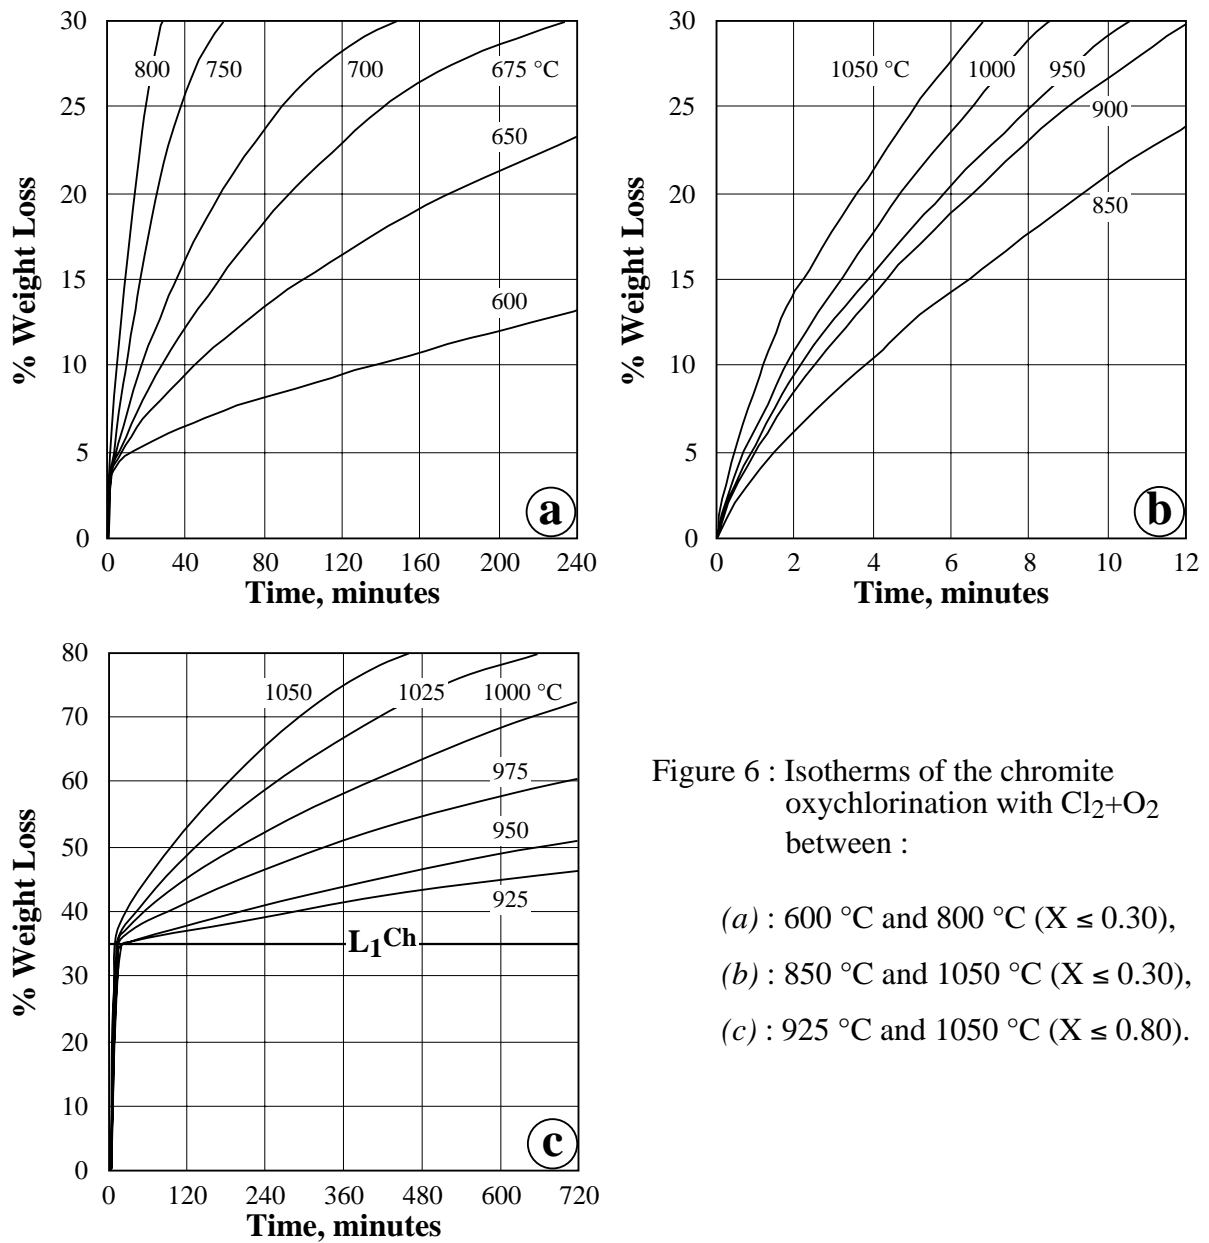


Figure 6 : Isotherms of the chromite oxychlorination with Cl_2+O_2 between :

- (a) : 600 °C and 800 °C ($X \leq 0.30$),
- (b) : 850 °C and 1050 °C ($X \leq 0.30$),
- (c) : 925 °C and 1050 °C ($X \leq 0.80$).

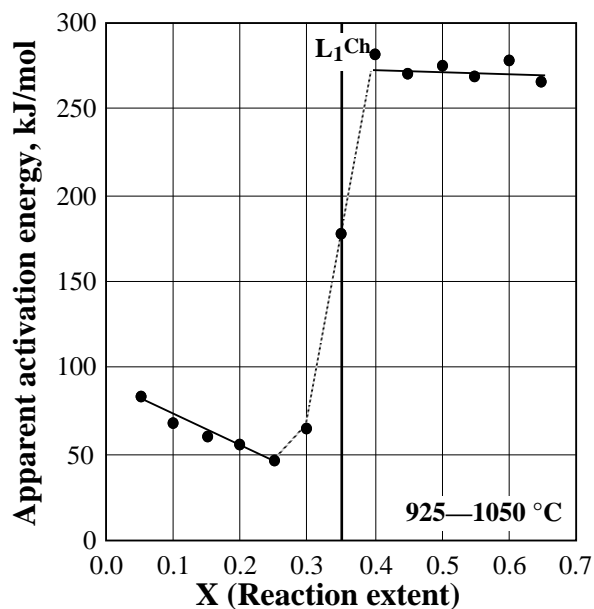


Figure 7 : Evolution of the activation energy as a function of the reaction extent.

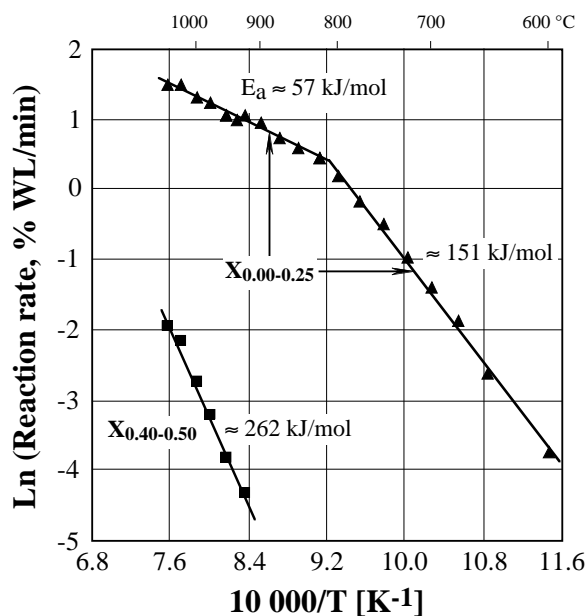


Figure 8 : Example of Arrhenius plot of the chromite oxychlorination.

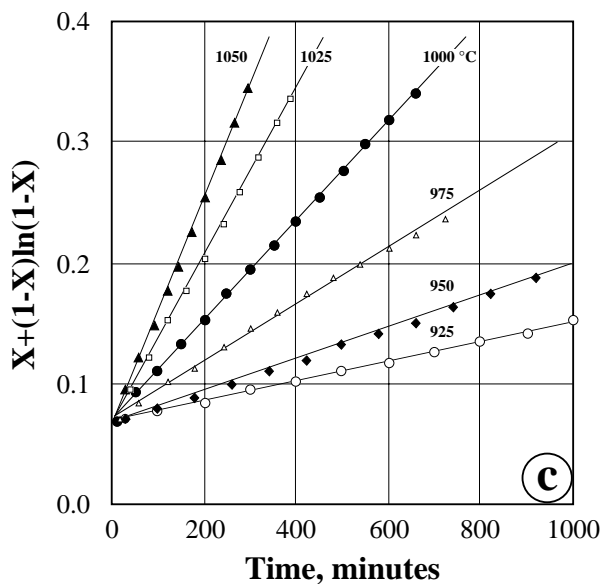
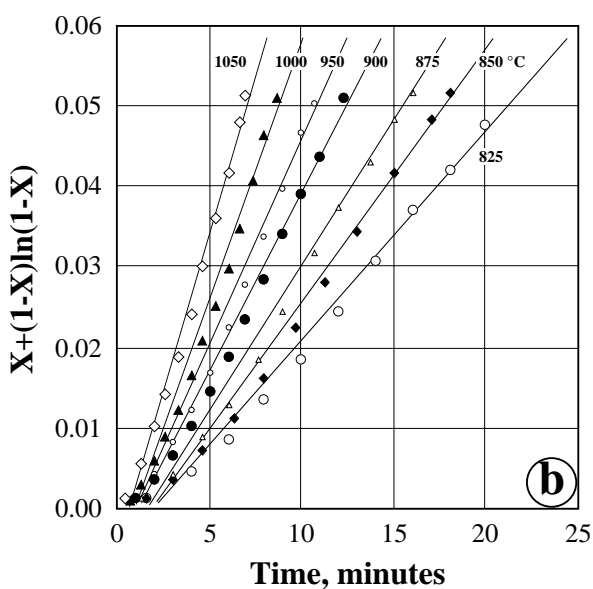
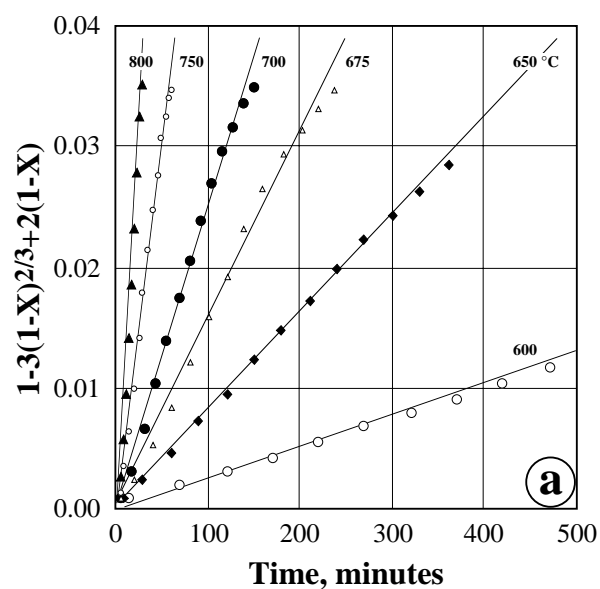


Figure 9 : Mathematical fitting of the data of the chromite oxychlorination for :

- (a) : $T \leq 800 \text{ }^{\circ}\text{C}$, $X \leq 0.30$ using Eq. [1],
- (b) : $T \geq 825 \text{ }^{\circ}\text{C}$, $X \leq 0.30$ using Eq. [2],
- (c) : $T \geq 925 \text{ }^{\circ}\text{C}$, $X \geq 0.35$ using Eq. [2].

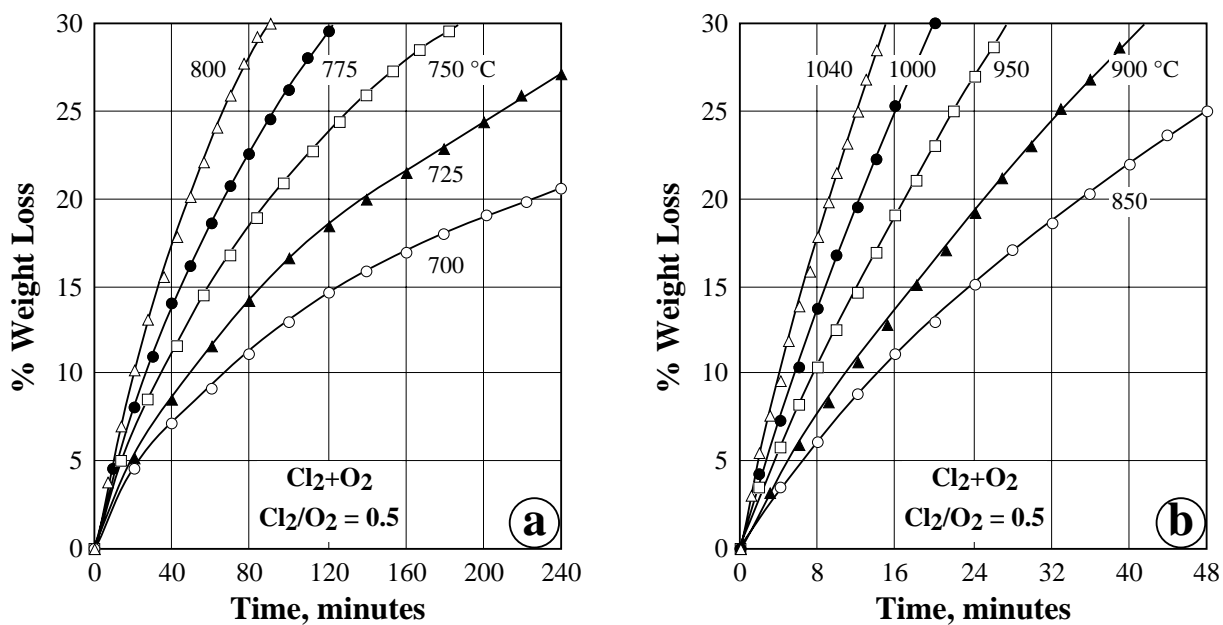


Figure 10 : Isotherms of the chromite oxychlorination with Cl_2+O_2 having a Cl_2/O_2 molar ratio equal to 0.5 for (a) $T \leq 800$ °C and (b) $T \geq 850$ °C.

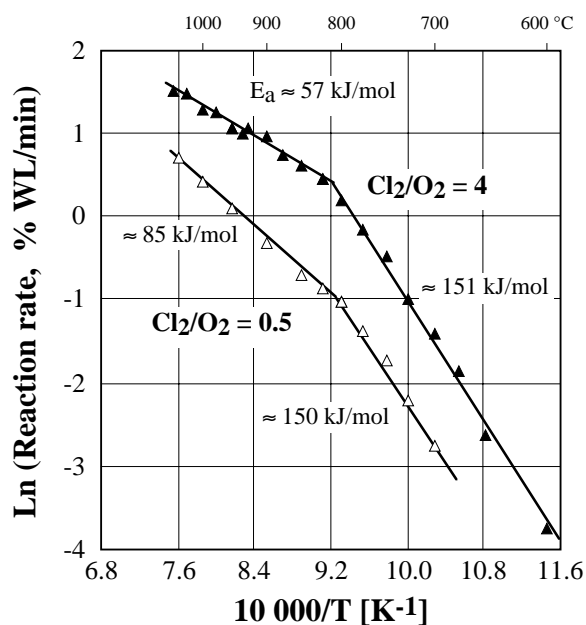


Figure 11 : Comparison of Arrhenius plots of the chromite oxychlorination with Cl_2+O_2 gaseous mixtures having different Cl_2/O_2 molar ratios.

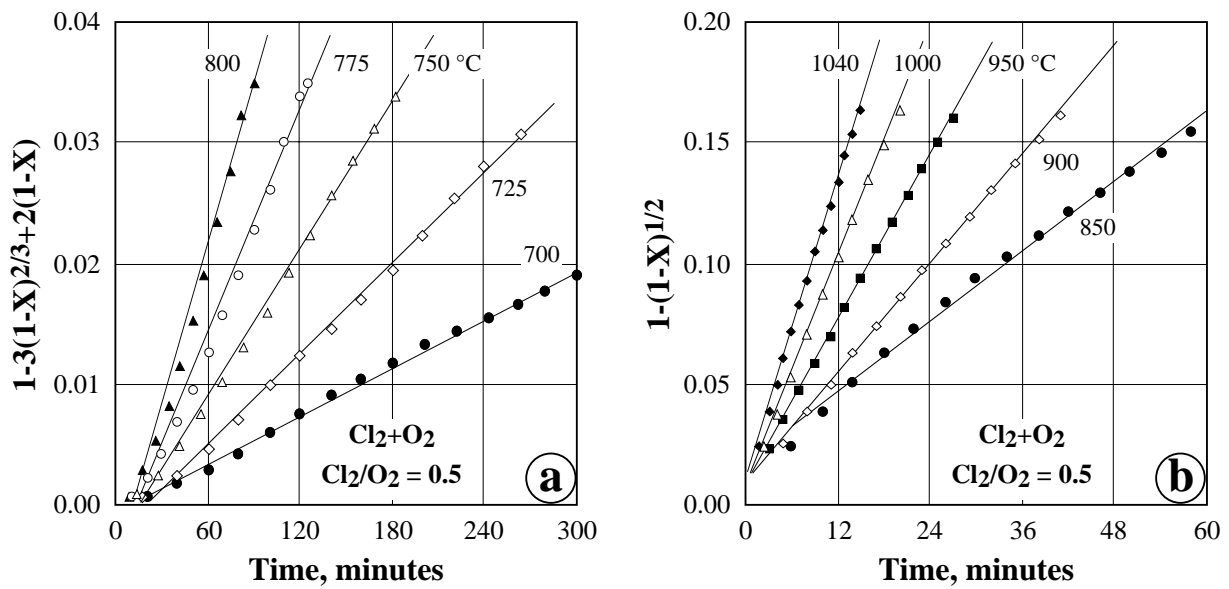


Figure 12 : Mathematical fitting of the oxychlorination data at (a) $T \leq 800$ °C and (b) $T \geq 850$ °C using Eqs. [1] and [3], respectively.

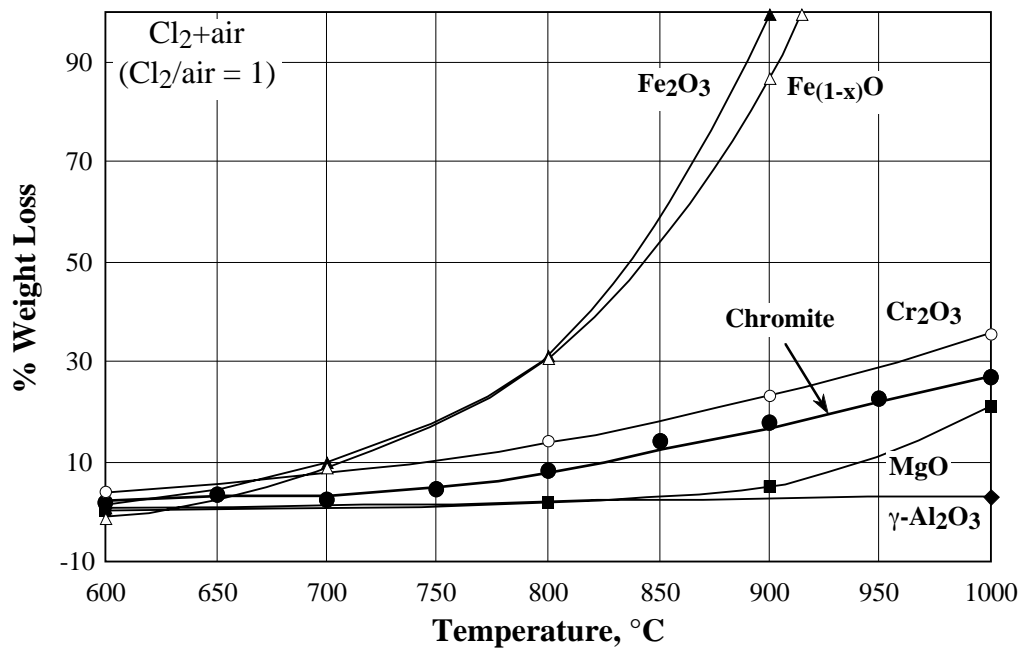


Figure 13 : Oxychlorination of chromite and its simple oxides with Cl_2 +air between 600 °C and 1000 °C for 2 hours using boat experiments.

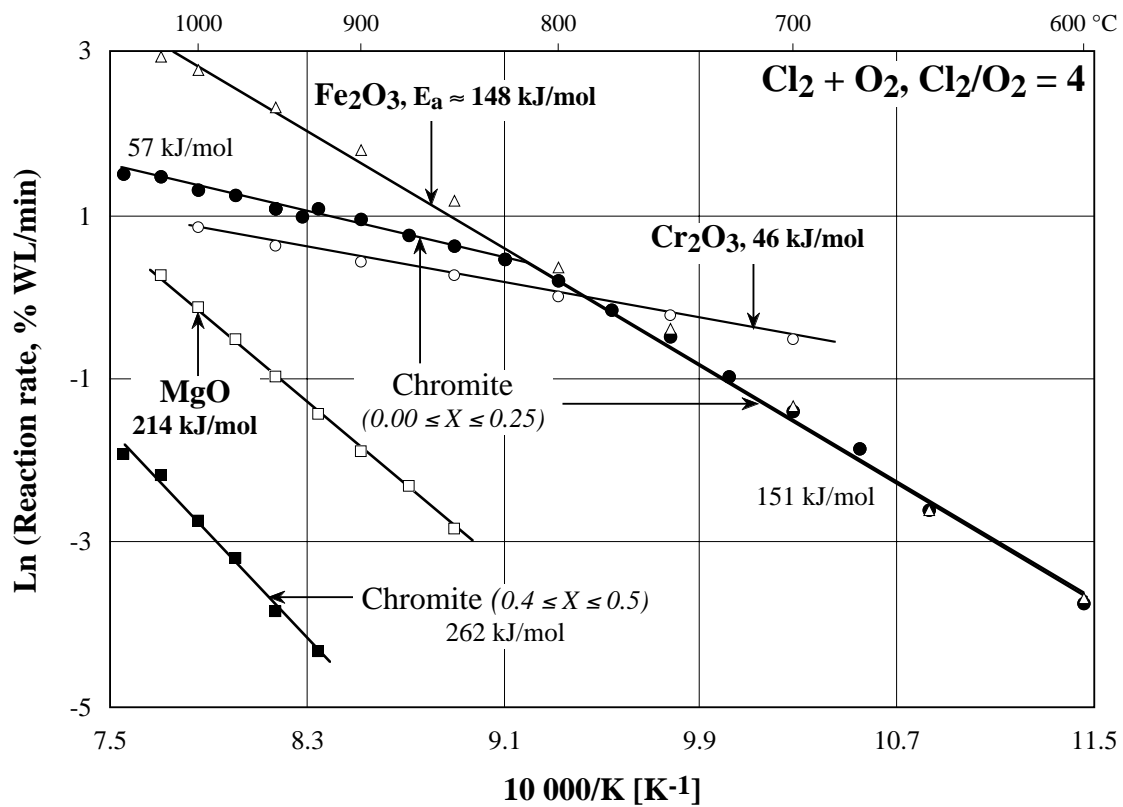


Figure 14 : Comparison of Arrhenius plots of the oxychlorination of chromite, Fe_2O_3 , Cr_2O_3 , and MgO .